



Assessment of natural radiation exposure from building materials in Estonia

Merle Lust* and Enn Realo

Institute of Physics, University of Tartu, Riia 142, 51014 Tartu, Estonia

Received 13 June 2011, accepted 30 September 2011, available online 21 May 2012

Abstract. Radionuclides naturally occurring in building materials may significantly contribute to the annual doses of the public. As information on the radioactivity of such materials is lacking, the study of building materials used in Estonia was carried out in order to estimate the annual dose to the Estonian population due to natural radionuclides in building materials. During the study 53 samples of commonly used raw materials and building products were collected and measured. The activity concentrations were determined by gamma ray spectrometry. Their mean values were in the ranges 7–747 Bq kg⁻¹ for ⁴⁰K, 4.4–69 Bq kg⁻¹ for ²²⁶Ra, and 0.8–86 Bq kg⁻¹ for ²³²Th. The activity index I in the 53 different building materials varied from 0.02 to 0.74 and the radium equivalent, from 6 to 239. The average annual dose for the people, caused by the building materials of dwellings, was assessed for most commonly used materials. It was estimated to be in the range from 0.16 mSv to 0.44 mSv.

Key words: radionuclides, building materials, dose assessment, gamma spectrometry.

INTRODUCTION

Man is continuously exposed to ionizing radiation from naturally occurring radioactive materials (NORM). The origin of these materials is the Earth's crust, but they find their way into building materials, air, water, food, and the human body itself. Measurement of activity concentrations of radionuclides in building materials is important in the assessment of population exposures, as most individuals spend 80% of their time indoors (Mustonen, 1985). Building materials cause direct radiation exposure, because most of them contain naturally occurring radioactive materials, mainly radionuclides from the ²²⁶Ra and ²³²Th decay chains and ⁴⁰K. The population-weighted average of indoor absorbed dose rate in air from terrestrial sources of radioactivity is estimated to be 84 nGy h⁻¹ (UNSCEAR, 2000). The worldwide average indoor effective dose due to gamma rays from building materials is estimated to be about 0.4 mSv per year (UNSCEAR, 1977, 1993). Elevated indoor external dose rates may arise from high radionuclide content in building materials (Chen and Lin, 1996; Stoulos et al.,

2003; Ahmed, 2005; Righi and Bruzzi, 2006; Brígido et al., 2008). Generally, natural building materials reflect the geology of their site of origin. The average activity concentrations of ²²⁶Ra, ²³²Th, and ⁴⁰K in the Earth's crust are 35, 30, and 400 Bq kg⁻¹, respectively. However, elevated levels of natural radionuclides causing annual doses of several mSv have been identified in some regions around the world, e.g. in Brazil, France, India, Nigeria, Iran (UNSCEAR, 1977, 1993, 2000). This external radiation exposure, caused by gamma-emitting radionuclides in building materials, can be assessed either by direct exposure measurements in the existing buildings or by radionuclide analyses of building materials with the dose rate modelling. Large-scale surveys of concentrations of radioisotopes in construction materials were summarized by the United Nations Scientific Committee on the Effects of Atomic Radiation, but very little information was found about conditions in Estonia. Consequently, the present study was undertaken with the purpose of determining radioactivity in some Estonian building materials and assessing the annual effective dose to the population due to external gamma ray exposure in dwellings typical of Estonia.

* Corresponding author, merle.lust@ut.ee

SAMPLE COLLECTION AND PREPARATION

During the last 10 years 53 samples of the building materials were analysed. Mostly, the sample selection consisted of the commonly available materials, which were obtained from the building material stores. All samples were crushed into grains, dried, homogenized, and put into metallic beakers. For the measurement a low-background ORTEC HPGe gamma spectrometer with a 42% efficiency and 1.7 keV resolution (at 1.3 MeV) was used.

For measurements the samples were placed into gas-tight containers with the capacity of 120 cm³. So after closure radon and thoron could not escape and during the ingrowth within about three weeks preceding the gamma spectrometric measurement a practical equilibrium between ²²⁶Ra and ²¹⁴Pb/Bi was achieved in the samples. For determination of the ²²⁶Ra and ²³²Th content the photopeaks of their daughters ²¹⁴Pb, ²¹⁴Bi and ²²⁸Ac, ²⁰⁸Tl, respectively, were used.

For the estimation of the efficiencies a set of high-quality certified reference materials, e.g. IAEA-RG-SET (K, Th, U), with densities similar to the building materials measured after pulverization and calculations were used. The efficiency calibration of the gamma spectrometry systems was performed with the radionuclide specific efficiency method in order to avoid any uncertainty in gamma ray intensities, as well as the influence of coincidence summation and self-absorption effects of the emitting gamma photons.

DOSE RATE ESTIMATION

The method used for estimation of the doses is based on the work presented by Mustonen (1985) and Markkanen (1995). The dose rate is calculated for a rectangular source of uniform density and activity concentration. The following geometry is used: wall w₁ 7 × 2.8 m², wall w₂ 12 × 2.8 m², floor and ceiling 7 × 12 m². The walls, floor, and ceiling are 0.2 m thick. The room has four windows (2 m × 1.2 m), located symmetrically in the shorter walls at a height of 80 cm from the floor. The gamma dose rate is calculated in the middle of the room presented in Fig. 1 (Markkanen, 1995). Several studies (Mustonen, 1985; Jong and Dijk, 2008; Al-Jundi et al., 2009) have proved that the variation in the dose rate is small (10–15%) and the dose rate in the middle of the room is a good approximation for the average dose rate in the room. It also appears that the dimensions of the room have only a relatively small effect on the dose rate in that room.

Dose rates from the ceiling, floor, and each wall are calculated separately and the total dose rate is calculated as their sum. The influence of windows is taken into account when calculating the dose rate from imaginary wall elements and it is subtracted from the total

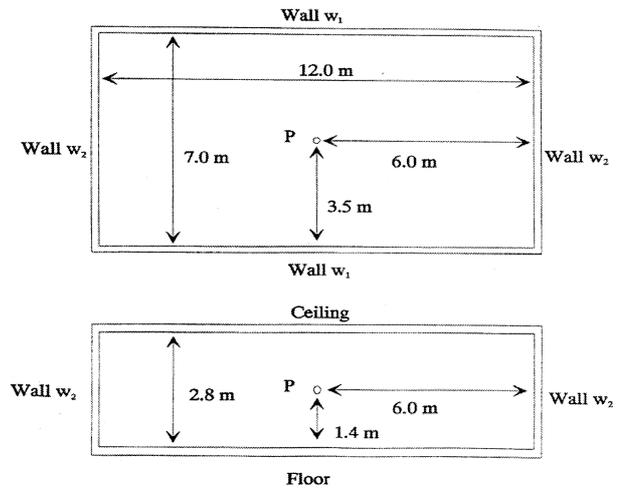


Fig. 1. The geometry used in calculation of the indoor gamma dose rate from building materials.

exposure rate. No external dose rate from the ground surrounding the room is taken into account. It is assumed that the annual exposure/occupancy time in dwellings is 7000 h. The conversion factor from the absorbed dose to effective dose is 0.7 Sv Gy⁻¹. The absorbed dose rate (Gy h⁻¹) in air at point P can be calculated according to the formula by Markkanen (1995):

$$D = 5.77 \times 10^{-7} \frac{C\rho}{4\pi} \sum \gamma_i \left(\frac{\mu_{en}}{\rho} \right)_i E_i \int B_i \frac{\exp(-\mu_i s)}{l^2} dV. \quad (1)$$

Two different layers of building materials can be considered in the dose assessment if proper build-up and attenuation factors are used.

The build-up factor according to the Berger model (Berger, 1957; Vruble, 1973) is

$$B_i = 1 + C(E_i) \mu_i s \exp(D(E_i) \mu_i s), \quad (2)$$

$$s = \left| \frac{z}{z_p - z} \right| l, \quad l = \sqrt{(x_p - x)^2 + (y_p - y)^2 + (z_p - z)^2}.$$

The parameters for equations (1) and (2) are as follows:

- C , activity concentration of the layer (Bq kg⁻¹);
- ρ , bulk density of the layer (kg m⁻³);
- γ_i , gamma intensity of gamma line i ;
- E_i , gamma energy of gamma line i (MeV);
- $(\mu_{en}/\rho)_i$, energy absorption coefficient in air for gamma energy E (cm² g⁻¹);
- μ , attenuation coefficient in the layer for gamma energy E (cm⁻¹);
- $C(E_i)$, coefficient in the Berger model;
- $D(E_i)$, coefficient in the Berger model;
- l , distance between the point P and the point of integration Q (cm);
- s , fraction of 1 within the layer (cm).

Table 1. Averaged gamma energies, attenuation coefficients in concrete, energy absorption coefficients in air, emission probabilities, and coefficients C and D in the build-up factors

Nuclide	Energy, keV	γ	μ_c , cm ⁻¹	μ_{en}/ρ_c , 10 ⁻⁵ cm ² g ⁻¹	C	D
²³⁸ U	810	2.12	0.166	0.0285	1.161	0.144
²³² Th	587	2.05	0.193	0.0295	1.279	0.190
²³² Th	2615	0.356	0.0927	0.0217	0.734	0.0234
⁴⁰ K	1461	0.107	0.124	0.0257	0.946	0.0755
¹³⁷ Cs	662	0.183	0.183	0.0293	1.237	0.1737

The average parameters used in dose assessments are given in Table 1 (Markkanen, 1995).

RESULTS AND DISCUSSION

The total number of material samples for the activity concentration measurement was 53. The measurement results are presented in Tables 2 and 3. In Table 2 the results of the most common building materials used for dwellings are given. Below these data are used for the estimation of public doses. For these materials at least

Table 2. Mean activity concentrations of radionuclides (Bq kg⁻¹) in the most commonly used building materials in Estonia

Material	²²⁶ Ra	²³⁸ U	²³² Th	⁴⁰ K
Aseri I brick	21.1±3.0	33.9±4.3	29.6±3.2	436±20
Aseri II brick	20.3±2.9	32.6±4.2	29.7±3.1	436±20
Aseri III brick	19.6±2.8	31.5±4.0	30.9±3.1	449±21
Misso Light brick	12.6±1.5	19.6±2.0	13.2±1.4	145±7
Misso Dark brick	18.4±2.4	28.8±3.2	19.4±2.2	207±9
Ash-blocks	27.3±2.3	28.5±2.2	14.1±1.7	308±8

Table 3. Mean activity concentrations of radionuclides (Bq kg⁻¹) in some building materials used in Estonia

Material	²²⁶ Ra	²³⁸ U	²³² Th	⁴⁰ K
Finnish building clay	53.6±3.4	56.3±3.3	58.5±3.2	748±17
Siimusti building clay	69.3±3.8	70.6±3.4	82.0±3.5	678±15
German building clay	35.6±2.3	36.9±2.1	55.2±2.4	447±11
Gypsum board	4.4±1.0	4.9±1.1	0.8±0.2	7.0±0.4
Grosso 311 floor tiles	64.1±3.8	48.4±2.4	81.5±2.8	344±9
Pronto 147 floor tiles	48.7±2.5	50.3±2.2	86.3±2.8	284±7
Kunda cement	46.9±2.8	49.0±2.5	21.4±1.6	587±13
Kolumbia stone	25.5±1.8	26.3±1.7	28.4±1.6	480±11
Concrete	35.1±2.1	36.1±1.8	11.3±0.9	207±5

five different samples were taken. Analysis results for other building materials which do not have a major impact on the annual public doses are given in Table 3.

Radionuclides present in the most commonly used building materials are of greater interest. The biggest differences occur in the concentration of ⁴⁰K, where the lowest mean value is 145 Bq kg⁻¹ for Misso Light and highest 449 Bq kg⁻¹ for Aseri III bricks. Much smaller variations are found for other radionuclides. From the results it can be seen that the lowest mean value of ²²⁶Ra concentration is 12.6 Bq kg⁻¹ measured in Misso Light clay brick, while the highest mean value for the same radionuclide is 27.3 Bq kg⁻¹ for oil-shale ash block.

The ALARA principle (the dose exposure indoors should be as low as reasonably achievable) for building materials is followed by using the index I . In a general case of a number x of different building materials in a room, the index is calculated as (OECD-NEA, 1979; EC, 1999)

$$I_{ext} = \sum_x \frac{\sum_{i=1}^n w_{mi} C_{x_i}}{A_x},$$

where x represents the nuclide of interest, n is the number of different kinds of buildings materials used in a room, C_{x_i} (Bq kg⁻¹) is the measured activity of each nuclide in the building material, w_{mi} is the weight fractional usage of the building material, i , and A_x (Bq kg⁻¹) is the parameter value representing the activity concentration of each nuclide of interest, which promoted an effective dose of 1 mSv per year.

For a specific building material the parameters A_x have the following values: 300 Bq kg⁻¹ for ²²⁶Ra; 200 Bq kg⁻¹ for ²³²Th, and 3000 Bq kg⁻¹ for ⁴⁰K. Accordingly, this index is defined by international as well as by the Estonian legislation (EC, 1999; Estonian Radiation Act, 2004) as the following sum:

$$I = \frac{C_{Th}}{200 \text{ Bq/kg}^{-1}} + \frac{C_{Ra}}{300 \text{ Bq/kg}^{-1}} + \frac{C_K}{3000 \text{ Bq/kg}^{-1}},$$

where C_{Th} , C_{Ra} , and C_K represent mean activity concentrations (Bq kg⁻¹) of the radionuclides ²³²Th (in equilibrium with its daughter nuclides), ²²⁶Ra (in equilibrium with its daughters), and ⁴⁰K.

If the value of the activity index, I , for a building material is 1 or less, the corresponding material can be used, with regard to radioactivity without restriction. If the value exceeds 1, the responsible party (producer or dealer) is required to assess the radiation exposure caused by the material and show specifically that the safety requirement is fulfilled. The guidance for construction materials does not usually include possible radon releases to the indoor air from building materials. The values of the activity concentration index depend

on the dose criterion and the mode and the quantity of the material used in a building. According to the recommendations by the European Commission (EC, 1999) for materials used in bulk amounts, the activity index should be less than 0.5. However, for superficial and other materials with restricted use the corresponding activity index should be between 2 and 6.

The radium equivalent concept allows a single index or number to describe the gamma output from different mixtures of uranium (i.e. radium), thorium, and ^{40}K in a material. The radium equivalent $\text{Ra}(\text{eq})$ in Bq kg^{-1} can be calculated as follows (OECD–NEA, 1979; El-Hussein, 2005):

$$\text{Ra}(\text{eq}) = A(\text{Ra}) + 1.43A(\text{Th}) + 0.077A(\text{K}),$$

where $A(\text{Ra})$ is the activity of ^{226}Ra (which is usually the same as that of ^{238}U) in Bq kg^{-1} , $A(\text{Th})$ is the activity of ^{232}Th in Bq kg^{-1} , and $A(\text{K})$ is the activity of ^{40}K in Bq kg^{-1} .

The index I and radium equivalent values for the most common building materials measured is presented in Table 4.

Clay bricks are widely used for construction of dwellings and their natural radionuclide content affects the population. As there is concern that some of the buildings will cause excessive radiation doses to the residents due to gamma rays emitted, the data obtained from our measurements were used for the estimation of the corresponding doses.

Table 4. Index I and radium equivalent values calculated for the measured building materials

Material	Index I	Radium equivalent $\text{Ra}(\text{eq})$
Aseri I brick	0.47	97
Aseri II brick	0.44	96
Aseri III brick	0.37	98
Misso Light brick	0.16	66
Misso Dark brick	0.23	62
Ash-blocks	0.26	64
Finnish building clay	0.72	196
Siimusti building clay	0.87	239
German building clay	0.54	149
Gypsum board	0.02	6
Grosso 311 floor tiles	0.74	207
Pronto 147 floor tiles	0.69	194
Kunda cement	0.46	123
Kolumbia stone	0.39	103
Concrete	0.24	67

The calculations of annual doses caused by the natural radionuclides present in the building materials of dwellings were performed using the MathCAD software. A rather conservative assumption that all construction elements of the room, e.g. walls, the ceiling and the floor, are made of the same material is accepted in calculations. As a result, the evaluated annual doses represent the maximum values for the corresponding building material. The evaluations are not made for the materials, e.g. the binding materials and tiles, which practically form a relatively small fraction of the construction element. The density of building materials used in calculations is taken equal to 2350 kg m^{-3} . The results are presented in Table 5. From the results it can be concluded that the total effective dose rate is less than 1 mSv per year in dwellings constructed from the building materials measured in the course of the present study.

Table 6 shows the mean values for ^{226}Ra , ^{232}Th , ^{40}K , and radium equivalent activity for all building materials under investigation in other countries. This table also lists the typical world average values for building materials (UNSCEAR, 1993) and soil (UNSCEAR, 2000). We can see that the concentrations of radionuclides in Estonian building materials in the present study are comparable to those suggested by similar studies in other countries. In Estonia, maximum concentration values were recorded in different building clays and cement and minimum ones in gypsum board. Table 7 gives annual effective doses (mSv) for natural radionuclide sources in concrete, calculated from mean activity concentrations for Estonia and for selected countries (UNSCEAR, 2000). The dose values in the table are given for the occupancy factor equal to 1.

Table 5. Total annual dose due to the natural radionuclides in the building materials

Material	Total annual dose, mSv
Aseri I brick	0.42
Aseri II brick	0.42
Aseri III brick	0.44
Misso Light brick	0.16
Misso Dark brick	0.23
Ash-blocks	0.25

Table 6. Range and mean values for ^{226}Ra , ^{232}Th , ^{40}K activity, and Ra(eq) (Bq kg^{-1}) for building materials under investigation in other countries

Country	^{226}Ra		^{232}Th		^{40}K		Ra(eq)	References
	Range	Mean	Range	Mean	Range	Mean		
Ireland	<1–140	32	<1–57	18	4–1977	353	–	Lee et al. (2004)
South Korea	6–27	–	<90	–	17–1081	–	–	Lee et al. (2001)
Sri Lanka	–	35	–	72	–	585	183	Hewamanna et al. (2001)
Pakistan	37–52	–	52–68	–	680–784	–	<370	Khan et al. (2002)
Nigeria	4–67	15.7	12–266	36	86–1073	253	100	Farai and Ademola (2005)
Jordan	10–340	116	3–210	64	2–1500	480	246	Ahmed (2005)
Turkey	18–59	–	7–20	–	66–249	–	–	Mavi and Akkurt (2010)
Malaysia	–	–	13–162	–	328–7541	–	79–1131	Ibrahim (1999)
World average for building materials	50	–	50	–	500	–	–	UNSCEAR (1993)
	35	–	30	–	400	–	–	UNSCEAR (2000)
Present work	4–69	33.5	1–82	37.5	7–678	384	118	

–, no data.

Table 7. Annual effective dose for natural radionuclide sources in concrete, calculated from mean activity concentrations for Estonia and for selected countries (UNSCEAR, 2000)

Country	Total annual effective dose, mSv
Greece	0.39
Egypt	0.41
Algeria	0.44
Switzerland	0.49
Russian Federation	0.49
United States	0.53
India	0.69
Sweden	0.78
Norway	0.86
Estonia	0.27

CONCLUSIONS

To control the indoor exposure caused by the ionizing radiation emitted from building materials, an accurate determination of their natural radioactivity is required. Assuming the ALARA principle, which requires that the indoor doses should be ‘as low as reasonably achievable’, the indices I have been proposed. These indices need to be considered in making decisions about the applicability of a building material in construction. Mean values of the index I of the studied building material samples range from 0.02 to 0.74, which means that all materials pass the accepted regulatory standards. The radium activity equivalent Ra(eq) values of the material samples range from 6 Bq kg^{-1} (gypsum board) to 239 Bq kg^{-1} (Siimusti building clay), both well below the value of 370 Bq kg^{-1} , which corresponds to an annual effective dose of 1 mSv.

The average effective dose annually received by the residents due to building materials varies from 0.16 to 0.44 mSv. Only a few doses are slightly larger than the

worldwide average annual external effective dose of 0.41 mSv from natural indoor radiation sources (UNSCEAR, 2010).

ACKNOWLEDGEMENTS

This work was partially supported by the graduate school ‘Functional materials and processes’ receiving funding from the European Social Fund under project 1.2.0401.09-0079 in Estonia. The authors would also like to thank the referees for their valuable comments.

REFERENCES

- Ahmed, N. K. 2005. Measurement of natural radioactivity in building materials in Qena city, Upper Egypt. *J. Environ. Radioact.*, **83**, 91–99.
- Al-Jundi, J., Ulanovsky, A., and Prohl, G. 2009. Doses of external exposure in Jordan house due to gamma-emitting natural radionuclides in building materials. *J. Environ. Radioact.*, **100**, 841–846.
- Berger, M. J. 1957. Calculation of energy dissipation by gamma radiation near the interface between two media. *J. Appl. Phys.*, **28**, 1502–1508.
- Brígido Flores, O., Montalvan Estrada, A., Rosa Suarez, R., Tomas Zerquera, J., and Hernandez Perez, A. 2008. Natural radionuclide content in building materials and gamma dose rate in dwellings in Cuba. *J. Environ. Radioact.*, **99**, 1834–1837.
- Chen, C. J. and Lin, Y. M. 1996. Assessment of building materials for compliance with regulations of ROC. *Environ. Internat.*, **22**, S221–S226.
- El-Hussein, A. 2005. A study on natural radiation exposure in different realistic living rooms. *J. Environ. Radioact.*, **79**, 355–367.
- Estonian Radiation Act. 2004.
- [EC] European Commission. 1999. *Radiation Protection 112. Radiological Protection Principles Concerning the*

- Natural Radioactivity of Building Materials*. Directorate-General, Environment, Nuclear Safety and Civil Protection.
- Farai, I. P. and Ademola, J. A. 2005. Radium equivalent activity concentrations in concrete building blocks in eight cities in Southwestern Nigeria. *J. Environ. Radioact.*, **79**, 119–125.
- Hewamanna, R., Sumithrachchi, C. S., Mahawatte, P., Nanayakkara, H. L. C., and Ratnayake, H. C. 2001. Natural radioactivity and gamma dose from Sri Lankan clay bricks used in building construction. *Appl. Radiat. Isot.*, **54**, 365–369.
- Ibrahim, N. 1999. Natural activities of ^{238}U , ^{232}Th and ^{40}K in building materials. *J. Environ. Radioact.*, **43**, 255–258.
- Jong, P. and Dijk, J. W. E. 2008. Calculation of the indoor gamma dose rate distribution due to building materials in the Netherlands. *Radiat. Prot. Dosim.*, **132**, 381–389.
- Khan, K., Aslam, M., Orfi, S. D., and Khan, H. M. 2002. Norm and associated radiation hazards in bricks fabricated in various localities of the North-West Frontier Province (Pakistan). *J. Environ. Radioact.*, **58**, 59–66.
- Lee, E. M., Menezes, G., and Finch, E. C. 2004. Natural radioactivity in building materials in the Republic of Ireland. *Health Phys.*, **86**, 378–383.
- Lee, S. C., Kim, C. K., Lee, D. M., and Kang, H. D. 2001. Natural radionuclides contents and radon exhalation rates in building materials used in South Korea. *Radiat. Prot. Dosim.*, **94**, 269–274.
- Markkanen, M. 1995. *Radiation Dose Assessments for Materials with Elevated Natural Radioactivity*. Report STUK-B-STO32. Radiation and Nuclear Safety Authority – STUK.
- Mavi, B. and Akkurt, I. 2010. Natural radioactivity and radiation hazards in some building materials used in Isparta Turkey. *Radiat. Phys. Chem.*, **79**, 933–937.
- Mustonen, R. 1985. Methods for Evaluation of Radiation from Building Materials. *Radiat. Prot. Dosim.*, **7**, 235–238.
- [OECD-NEA] Organization for Economic Co-operation and Development–Nuclear Energy Agency. 1979. *Report Exposure to Radiation from Natural Radioactivity in Building Materials*. Paris.
- Righi, S. and Bruzzi, L. 2006. Natural radioactivity and radon exhalation in building materials used in Italian dwellings. *J. Environ. Radioact.*, **88**, 158–170.
- Stoulos, S., Manolopoulou, M., and Papastefanou, C. 2003. Assessment of natural radiation exposure and radon exhalation from building materials in Greece. *J. Environ. Radioact.*, **69**, 225–240.
- [UNSCEAR] United Nations Scientific Committee on the Effects of Atomic Radiation. 1977. *Sources, Effects and Risks of Ionizing Radiation*. Report to the General Assembly with Annex B: Natural Sources of Radiation. United Nations, New York.
- [UNSCEAR] United Nations Scientific Committee on the Effects of Atomic Radiation. 1993. *Sources and Effects of Ionizing Radiation*. United Nations, New York.
- [UNSCEAR] United Nations Scientific Committee on the Effects of Atomic Radiation. 2000. *Sources, Effects and Risks of Ionizing Radiation*. 2000 Report to the General Assembly with Annex B: Exposures from Natural Sources of Radiation. United Nations, New York.
- [UNSCEAR] United Nations Scientific Committee on the Effects of Atomic Radiation. 2010. *Sources and Effects of Ionizing Radiation*. 2008 Report to the General Assembly, with scientific annexes. United Nations, New York.
- Vrubel, M. N. 1973. Build-up factors of scattered radiation from point source in an unbound air medium. *Soviet At. Energy*, **34**, 63–65.

Ehitusmaterjalides leiduvatest looduslikest radionukliididest põhjustatud elanikudoosi hinnang

Merle Lust ja Enn Realo

Ehitusmaterjalides leiduvad looduslikud radionukliidid võivad olla väga olulisteks elanikudoosi tekitajateks. Käesoleva uurimistöö raames määrati looduslike radionukliidide sisaldus 53 erinevas Eestis kasutatava ehitusmaterjali proovis. Analüüsil kasutati kõrge eraldusvõimega HPGe gamm-spektromeetrit analüüsimeetodit. Leiti, et looduslike radionukliidide ^{40}K , ^{226}Ra ja ^{232}Th aktiivsuse kontsentratsioonid varieeruvad uuritud ehitusmaterjalides järgmistes vahemikes: vastavalt 7–747 Bq kg⁻¹, 4,4–69 Bq kg⁻¹ ning 0,8–86 Bq kg⁻¹. Aktiivsuse kontsentratsioonide alusel hinnatud ehitusmaterjalide aktiivsuseindeksi I väärtused asuvad piirides 0,02 kuni 0,74. Levinumate ehitusmaterjalide jaoks tehti doosihinnangud siseruumides ja selle alusel saadud aastased elanikudoosid jäävad vahemikku 0,16–0,44 mSv.